

R. Pinto^a, F. Oliveira^b, J. Borges^c, N. Correia^a^a INEGI, Instituto de Ciência e Inovação em Eng. Mecânica e Eng. Industrial, Porto 4200, Portugal^b CICECO, Instituto de Materiais de Aveiro, Aveiro 3810, Portugal^c CINAMIL, Centro de Investigação da Academia Militar, Lisboa, Portugal

Soluciones balísticas multimateriales para UAVs

RESUMEN

Historia del artículo:

Recibido 5 de Mayo 2019

En la versión revisada 20 de Junio 2019

Aceptado 5 de Julio 2019

Accesible online 18 de Enero de 2021

Palabras clave:

Materiales Compuestos

Modelado numérico

Impacto Balístico

Compuestos Híbridos

Impacto de Alta Energía

Uno de los principales desafíos para los Vehículos Aéreos no Tripulados (VAnT) utilizados en defensa y operaciones militares, es concluir efectivamente una misión de vuelo en entorno hostil. La capacidad de supervivencia de la plataforma es crítica. Es imperativo que el vehículo sea capaz de resistir impactos balísticos durante el vuelo y aún así llegue a su destino.

En el presente trabajo, los autores discuten el desarrollo de una armadura balística ligera para proteger áreas críticas del vehículo, como los sistemas de control o la carga útil. La respuesta de la estructura durante y después de un impacto de bala de 9 mm, muestra que los paneles compuestos híbridos propuestos serán capaces de resistir impactos balísticos de alta energía después de su optimización.

El método AEF (Análisis de Elementos Finitos) se implementa para estudiar el desempeño de las placas protectoras de cerámica unidas a la plataforma estructural PRFC (Polímero Reforzado con Fibra de Carbono). Se implementa una técnica de modelado euleriano-lagrangiano con diferentes modelos de daños para los diversos materiales involucrados en el evento de impacto con el fin de capturar adecuadamente cada respuesta material en el escenario de impacto.

Los estudios numéricos son validados experimentalmente. El PRFC estructural se cura en autoclave seguido de un postcurado para integrar los componentes restantes. Pruebas experimentales en un campo de tiro donde se disparan proyectiles de 9 mm a una distancia de 10 m de las placas objetivo a sido realizadas. Los modelos numéricos muestran una buena correlación con los datos experimentales.

Multimaterial ballistic solutions for UAVs

ABSTRACT

Keywords:

Composite materials

Numerical modelling

Ballistic impact

Hybrid composites

High energy impact

One of the main challenges for UAVs (Unmanned Aerial Vehicles) used in defence and military operations is to effectively conclude a flight mission in a harsh environment. The platform survivability is critical, therefore it is imperative that the vehicle is able to withstand ballistic impacts in flight and still be able to reach its destination.

In the present work, the authors discuss the development of a lightweight ballistic armour to protect critical areas of the vehicle, such as the control systems and/or the payload. The structure response during and after a 9 mm bullet impact, shows that the proposed hybrid composite panels will be able to withstand high-energy ballistic impacts after optimization.

The FEA (Finite Element Analysis) method is implemented to study the performance of ceramic protective plates attached to the CFRP (Carbon Fibre Reinforced Polymer) structural platform. An Eulerian-Lagrangian modelling technique is implemented with different damage models for the various materials involved in the impact event in order to properly capture each material response in this complex load scenario.

Numerical studies are validated experimentally. The base structural CFRP is cured in autoclave followed by a post-cure to integrate the remaining components. Experimental tests were conducted at a shooting range where 9 mm projectiles are fired at a distance of 10 m of the target plates. Data is collected recurring to a chronograph/high speed camera combination apparatus to measure the impact and residual velocity and the projectile deformation/damage. Numerical models show good correlation with the experimentally measured data.

1 Introduction

With the increased use of composite materials in aircraft structures, impact protection is also growingly important as these materials, which are lighter and more efficient than their metal counterparts, are more prone to impact damage, potentially reducing system performance. This topic is of particular interest in unmanned flight systems that carry payloads to and from harsh environment locations which are prone to ballistic impacts. It is imperative that the vehicle is able to complete the flight cycle and, therefore, the integrity of the flight control systems is of the highest importance in order to keep the vehicle in-service. This means that the structure, or at least the vicinity of the flight control systems, must be able to sustain ballistic impacts whilst maintaining the flight control. Design of such structural components is linked to the proper understanding of the materials used in an impact tolerant solution. The proposed approach in this investigation is to identify potential materials to resist an impact from a high energy projectile that may be coupled with the base structural composite material and still result in a low weight increase of the structure. The implemented methodology in the design and validation process is to subject the selected composites, as well as the combination of the composite and protective layer materials to ballistic impacts in a controlled environment. Numerical material models that capture the material behaviour in this extreme loading scenario, are developed and validated with the experimental data. This investigation looks at a ceramic based material to act as the protective agent over a load carrying carbon fibre reinforced polymer (CFRP) plate, responsible for the structural stability of the aircraft. Different modeling techniques are implemented as well as several damage models which are addressed to find the most suitable combination for the present mechanical solicitation scenario.

1.1 Background

A multi-layered ballistic armour consists of the combination of different materials with specific functions. Generally, a ballistic armour incorporates a ceramic layer, a backing composite laminate and, in some cases, a spall shield (covering the ceramic). A ceramic layer is normally placed on the strike face, preferably perpendicular to the expected threat [1]. High-performance ceramic materials, such as alumina (Al_2O_3), silicon carbide (SiC), boron carbide (B_4C) or silicon nitride (Si_3N_4) [2], are renowned for their high hardness and strength and relatively low brittleness, when compared with other ceramics. Therefore, they are responsible for shattering the bullet and absorbing the primary impact energy [3]. The protective armour material can incorporate a single or multiple ceramic elements (multi-piece). The use of multiple ceramic components, usually triangles, squares or hexagons, allows for a much wider range of configurations, such as multi-curved and complex geometries [2], [4]. Additionally, the integration of smaller tiles promotes the protection against multi-impacts, although this can be affected by the type of interface. The ceramic components can be directly abutted or some distance between them can be kept with or without damping material at the joint [4]. Statistically, interfaces associated to the incorporation of hexagonal ceramic elements have a slightly lower impact vulnerability than those with the other geometries [5].

The energy dissipation mechanism is associated not only to the projectile spalling but also to the ceramic fragmentation [6], [7]. In order to ensure the bullet remaining kinetic energy absorption, a single or multiple backing layers are added to the armour [6], [8].

In the modern ballistic armours, a composite layer usually supports the ceramic tile(s). UHMWPE and Kevlar composites are commonly used as armour backing layers due to their outstanding impact shock wave absorption capacity [6]. Carbon and glass fibre composites can also be a viable solution in some specific situations. Such an example is if the structural integrity or cost are a priority.

Regarding the spall shield, it covers the ceramic front surface and protects the component and the armour itself from the fragments blast. It may be a synthetic plastic sheath, a thermoplastic sheath, a polycarbonate sheath or a polymer-encased reinforcement layer (e.g. high tensile strength fine steel wire mesh or glass fibre embedded in a polymer). Self-sealing materials such as vulcanized rubber, including polyurethane elastomers and silicone, are also commonly used. These materials are able to close upon a punctured hole created by the incoming projectile and thus the size of the hole is smaller than the size of the ceramic tiles; this contributes to the ceramic protection [1], [9], [10].

2 Materials and processes

2.1 Carbon fibre reinforced polymer plates

The structural base CFRP material chosen for this investigation was HS300/ER563 UD composite. The stacking sequence was $[\text{90}_2, \text{0}_2, \text{90}_2]_s$ for a total of 12 plies. The $200 \times 200 \text{ mm}^2$ plates were cured in an autoclave following the manufacturer's instructions resulting in a final cured thickness of 3.64 mm.

2.2 Ceramic plates

The ceramic plates were pressureless sintered in a N_2 atmosphere. Hexagonal plates were produced using two different powder sources: 1) Commercially available spray dried Si_3N_4 powder with sintering aids and organic binders. 2) An in-house developed matrix formulation, using Al_2O_3 and Y_2O_3 sintering aids. After pressing, the samples were heated in an oven to remove the organic compounds (calcination). Both the samples from the commercial powder and the matrix were sintered inside a crucible filled with a powder bed to prevent decomposition (50 % matrix powder + 50 % of BN powder). The sintering temperature of the hexagonal samples was $1700 \text{ }^\circ\text{C}$ / 3 h dwell time. The resulting ceramic hexagons had an average thickness of 3.8 mm.

2.3 Processing the multi-material solution

The ceramic hexagons were manually placed on top of the CFRP plates using a MTC510 epoxy adhesive film in between. The assembly was then subjected to a post-cure in the autoclave following the adhesive film manufacturer's instructions (Figure 1). Of note that this post-cure is performed at a lower temperature and pressure of those needed to process the base materials (CFRP and ceramic).





Figure 1. CFRP control plate (left) and CFRP plate with bounded ceramic hexagons on top (right).

3 Experimental test campaign

Two groups of samples were subjected to experimental ballistic tests in controlled environment in a total of 6 tested samples; 3 composed only of CFRP material (base group) and another 3 that had the ceramic hexagons bounded to the CFRP base plate. The projectiles were 9 mm lead bullets fired at a distance of 10 m of the target. Impact velocity was measured by means of a laser chronograph and residual velocity with a high speed camera. The average impact speed considering all tests was 335 m/s and the residual speed was 333 m/s and 164 m/s for the CFRP and the CFRP-ceramic plates, respectively.

4 Numerical models

The finite element commercial package Abaqus® was used to perform all numerical investigations. The Eulerian-Lagrangian method was employed to model the different components/materials, where the CFRP and ceramic are modelled as 3D Lagrangian elements and the bullet as Eurlian with no casing and implemented having lead as the material.

The MTC510 epoxy adhesive film, between the CFRP and the CFRP, is modeled using two different cohesive law techniques, by means of 3D cohesive elements or using a cohesive contact formulation. A similar approach is adapted to capture the ceramic behaviour where the material model implemented was the JHB or the JH-2 [11] applied to C3D8R elements. Finally, the CFRP is modelled using C3D8R elements, an extrapolation of the Hashin failure criteria [12] to 3D was implemented for the this material, with no damage propagation, by means of a VUMAT user subroutine. The bullet is modeled as an elastic/plastic medium using Eurlian mesh elements.

Table 1, 2, 3 and 4 summarize the material properties necessary for each component as per each respective chosen damage criteria and Figure 2 shows a schematic of the numerical test apparatus.

Table 1. HS300/ER563 UD CFRP elastic and strength properties.

Property	Value	Unit
Density	1.60 x 10 ³	ton/mm ³
E ₁	139600	MPa
E ₂ / E ₃	8665.93	MPa
ν ₁₂ / ν ₁₃	0.26	--
ν ₂₃	0.38	--
G ₁₂ / G ₁₃	3610.80	MPa
G ₂₃	2145.76	MPa
X _t	2740	MPa
X _c	2107.20	MPa
Y _t / Z _t	37.47	MPa
Y _c / Z _c	137.77	MPa
S ₁₂ / S ₁₃ / S ₂₃	46.36	MPa

Table 2. MTC510 epoxy adhesive film cohesive properties.

Property	Value	Units
Density	1.59 x 10 ³	ton/mm ³
E / E _{nn}	1.0 x 10 ⁶	(high number)
G ₁ / E _{ss}	1.0 x 10 ⁶	(high number)
G ₂ / E _{tt}	1.0 x 10 ⁶	(high number)
Nominal stress	60	MPa
Nominal stress 1 st and 2 nd directions	55	MPa
Normal mode fracture energy	0.489	N/mm
Shear mode fracture energy 1 st and 2 nd directions	0.31	N/mm
Viscosity coefficient	1.0 x 10 ⁻⁵	

Table 3. Ceramic properties required for JHB and JH-2 formulations.

Property	Value	Units
Density	3.23 x 10 ³	ton/mm ³
G	120000	MPa
A; N; B; M	0.96; 0.65; 0.35; 1	--
C; e0	0.009; 1	
T	800	MPa
g _{i_max} ; g _{f_max}	1.24; 0.13	--
HEL	11700	MPa
p_HEL	5130	MPa
beta; D1; D2	1; 0.48; 0.48	N/mm
epl_max; epl_min; FS	1.2; 0; 0.2	N/mm
K1; K2; K3	220000; 361000; 0	MPa

Table 4. Lead elastic and plastic properties for Eurlian formulation.

Property	Value	Units
Density	1.13 x 10 ³	ton/mm ³
Young's modulus	13800	MPa
Poisson coefficient	0.42	--
Yield stress	5 @ 5%	MPa
Strength	18 @ 75%	MPa

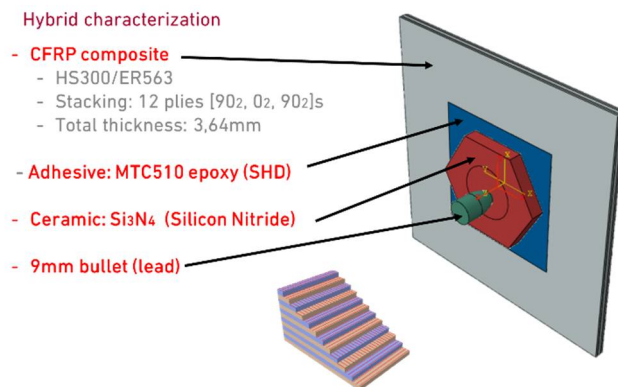


Figure 2. Schematic of the target showing the different layers of material and representation of the bullet.

5 Results and discussion

The model response to a ballistic impact event for the CFRP and for the CFRP-ceramic hybrid plates is depicted in Figures 3 and 4. As can be observed, the bullet almost suffers no deformation impacting the CFRP plate and the damaged area is very limited to the area where there is penetration. The opposite occurs when the bullet penetrates the CFRP-ceramic plate where it significantly deforms, since most of the energy is dissipated in the ceramic material therefore, less energy is left in the projectile, nevertheless this remainder of energy is enough to pass through the fibers of the CFRP but, since the energy is lower, it is dissipated in an area considerably larger.



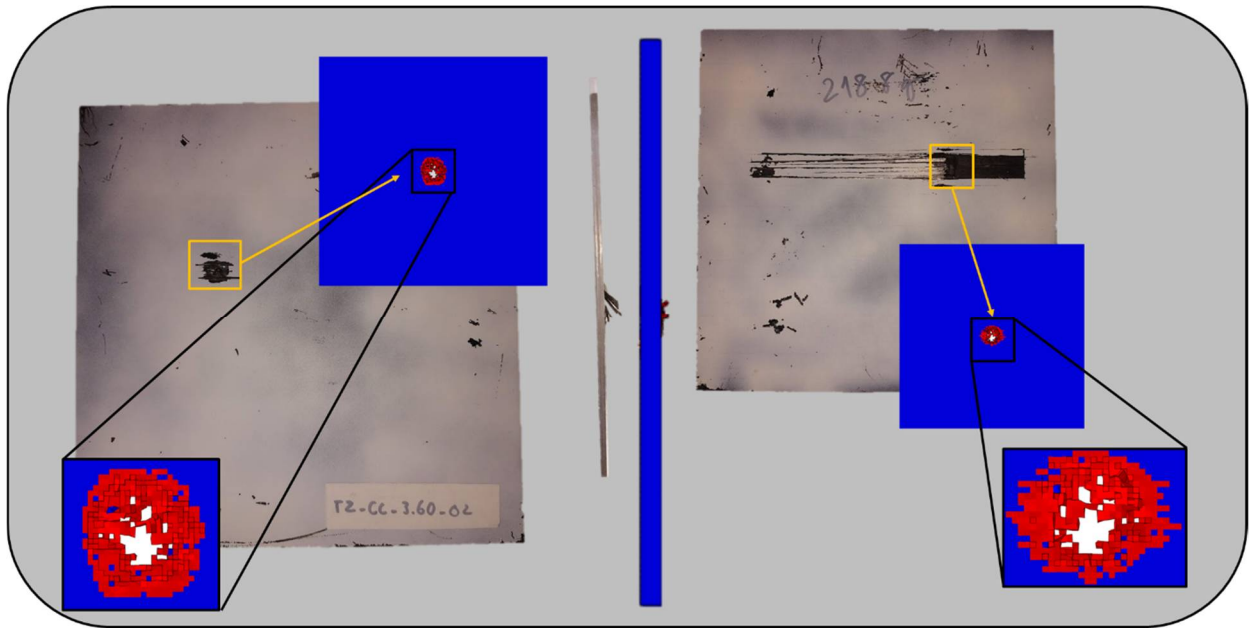


Figure 5. CFRP experimental and numerical results showing the bullet entry point (on the left) and exit hole (on the right).

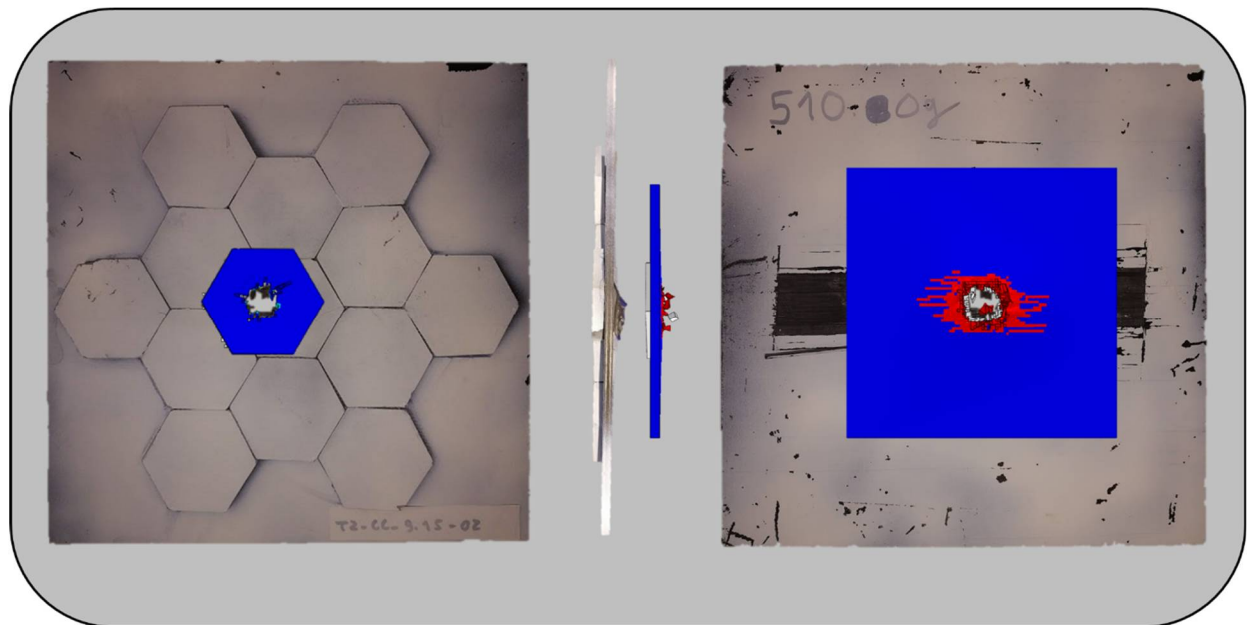


Figure 6. CFRP+ceramic experimental and numerical results.

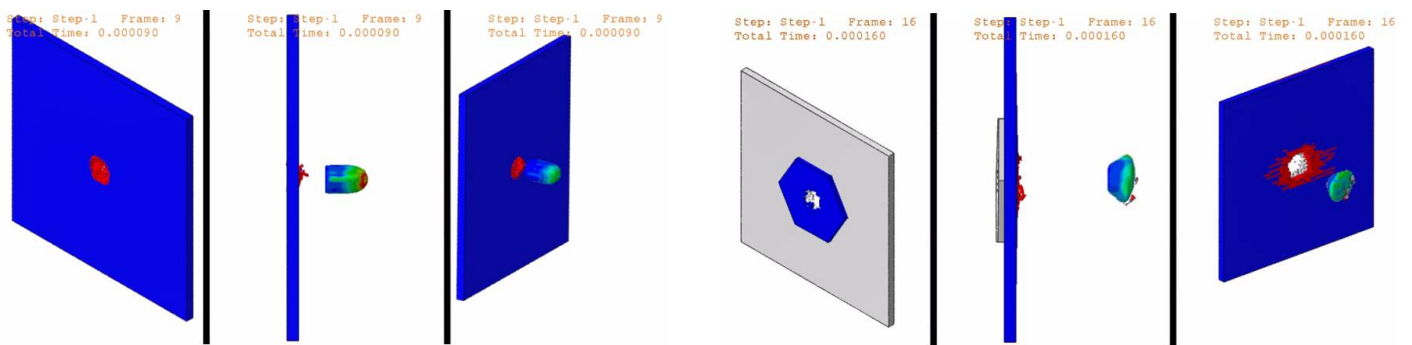


Figure 3. Numerical model of the bullet penetrating the CFRP, depicting the damage in the HS300/ER563 material and bullet plastic deformation from different angles (entry side – left, side view – middle and exit side - right).

Figure 4. Numerical model of the bullet penetrating the CFRP-ceramic, depicting the damage in the HS300/ER563 and ceramic materials and the bullet plastic deformation from different angles (entry side – left, side view – middle and exit side - right).



Table 7 and 8 summarize the results of the experimental measurements and the residual velocity obtained with the numerical models. Figure 5 and 6 show the experimental results overlapped with the numerical data for the CFRP plate and for the CFRP plate with ceramic protection respectively. There is good correlation between the model and the experimental results when comparing the residual velocities.

Table 5. Summary of the experimental test data.

Formulation	Initial velocity	Residual velocity
CFRP	335 m/s	333 m/s
CFRP + ceramic	335 m/s	164 m/s

Table 6. Summary of the FEA numerical models.

Formulation	Cohesive contact	Cohesive 3D elements
CFRP	328 m/s with no cohesive formulations	
CFRP + ceramic JHB	251 m/s	280 m/s
CFRP + ceramic JH-2	162 m/s	143 m/s

As can be observed, some modeling techniques are able to capture the residual velocity / energy properly, where others are inadequate. For the scenario under investigation, the modeling approach used to capture the impact of the bullet on a HS300/ER563 UD composite CFRP plate by means of the Hashin failure criteria using 3D C3D8R elements, has shown that there is excellent correlation between the model and the experimental results with a difference of only 1.5 % when comparing the average of the experimentally measured residual velocity (333 m/s) and the value determined using the finite element method (328 m/s).

With the hybrid solution results and analysis, i.e. ceramic hexagonal tiles integrated into the CFRP plate, one can observe that the modeling solution that has better correlation with the experimental data is a combination of using a cohesive contact formulation, between the ceramic tiles and the CFRP plate, and implementing the JH-2 ceramic damage model to the hexagonal tile keeping the same modeling technique as discussed previously for the CFRP plate. The average of the measured experimental velocity was 164 m/s and the value determined in the aforementioned modeling scenario was 162 m/s, this represents a difference of 1.2 % of error between the numerical model and the experimental results.

6 Conclusions

It is shown that the implemented models are able to properly capture the residual velocity for the two impact scenarios under investigation for a hybrid material solution which involves different material models and modeling techniques. It is clear that for the purpose of design, a thicker plate is required to avoid penetration of the structure of the aircraft. Nevertheless the projectile speed was decreased by about 51 % (from 335m/s to 164m/s in average) when using a 3.8 mm ceramic plate. Of course this increase in thickness poses a challenge since, more material directly translates to an increase in weight.

7 Future work

The only assessed variable in the present work was the residual velocity. Nevertheless, it is highly important to address the

damage extension in the structural components for impact scenarios where there is complete penetration of the structure and when the projectile is stopped inside the material. In particular, the case where the bullet is stopped inside the material, it is expected that damage by delamination is responsible for dissipating a high level of projectile energy. Therefore it is expected that modeling the interply sections of the CFRP will be a requirement to capture this failure mechanism.

It was concluded that thicker ceramic tiles are needed to stop the projectile, however the direct increase in weight of the solution may render it invalid. The weight is of high importance in the current aircraft industry segment. Nevertheless, the intrinsic capacity of the ceramic to shatter the projectile upon impact makes it imperative in the use as the first line of defense in the present protection systems. Therefore, the investigators believe that the solution will be a combination of more materials, keeping the present ceramic thickness, and having a second layer made out of HB26 or another emerging material, for example. This will allow to increase the thickness, the energy absorption capability, and absorb part of the deformation of the ceramic. Nevertheless HB26 implementation brings a new layer of complexity to the models since it is a fabric. Regardless of these suppositions and suggestions future investigation needs to be carried out in this direction to find the optimal balance between cost and weight of the solution and should always be tailored and optimized to the design requirements.

Acknowledgements

Authors gratefully acknowledge the funding of Project POCI-01-0247-FEDER-017751 – ALIR_mcs, cofinanced by Programa Operacional Competitividade e Internacionalização (Compete 2020), through Fundo Europeu de Desenvolvimento Regional (FEDER)."

References

- [1] CeramTec - ETEC GmbH, "Ceramic Materials for light-weight Ceramic Polymer Armor Systems."
- [2] J. Jiusti *et al.*, "Ballistic performance of Al₂O₃ mosaic armors with gap-filling materials," *Ceram. Int.*, vol. 43, no. 2, pp. 2697–2704, Feb. 2017.
- [3] E. Medvedovski, "Advances in Applied Ceramics Structural, Functional and Bioceramics Lightweight ceramic composite armour system Lightweight ceramic composite armour system," 2013.
- [4] L. Bracamonte, I. K. Yilmazcoban, and R. Loutfy, "Design, manufacture, and analysis of ceramic-composite armor," in *Lightweight Ballistic Composites: Military and Law-Enforcement Applications*, 2nd ed., 2016, pp. 349–367.
- [5] S. J. Bless and D. L. Jurick, "Design for Multi-hit Capability," *Int. J. Impact Eng.*, vol. 21, no. 10, pp. 905–908, 1998.
- [6] E. Medvedovski, "Ballistic performance of armour ceramics: Influence of design and structure. Part 1," *Ceram. Int.*, vol. 36, no. 7, pp. 2103–2115, Sep. 2010.
- [7] F. Santos da Luz, E. P. L. Junior, L. H. L. Louro, and S. N. Monteiro, "Ballistic Test of Multilayered Armor with Intermediate Epoxy Composite Reinforced with Jute Fabric," *Mater. Res.*, 2015.
- [8] W. Liu *et al.*, "Influence of different back laminate layers on



- ballistic performance of ceramic composite armor," *Mater. Des.*, vol. 87, pp. 421–427, 2015.
- [9] Lucuta, "Ceramic Armour Systems with a Front Spall Layer and a Shock Absorbing Layer," US 6912944 B2, 2005.
- [10] I. Moore, "Encapsulated Ceramic Composite Armour," US 7866248 B2, 2011.
- [11] T. J. Holmquist and G. R. Johnson, "Characterization and evaluation of silicon carbide for high-velocity impact," *J. Appl. Phys.*, vol. 97, no. 9, p. 093502, May 2005.
- [12] Z. Hashin and A. Rotem, "A Fatigue Failure Criterion for Fiber Reinforced Materials," *J. Compos. Mater.*, vol. 7, no. 4, pp. 448–464, Oct. 1973.

