

# ADDITIVE EDGE BINDING LAYERS TO SUPPRESS FREE-EDGE DELAMINATION UNDER TENSILE LOAD

Miguel Ubago Torres<sup>1\*</sup>, Meisam Jalalvand<sup>2</sup>

<sup>1</sup> Advance Composites Group (ACG), Department of Mechanical and Aerospace Engineering, University of Strathclyde, Glasgow, United Kingdom

<sup>2</sup> Engineering Materials, Department of Mechanical Engineering, University of Southampton, Southampton, UK

\* miguel.ubago-torres@strath.ac.uk

An additive laminate applied to the free-edges of cured composite laminates was used for stopping delamination in laminates under tension. The solution was examined on an angle-ply substrate laminate (AP laminate) susceptible to delamination with a layup of  $[(20_2/-20_2)]_s$ . Numerical analyses were conducted to determine the effectiveness of this technique and the experimental results proved that the free-edge delamination was successfully suppressed.

A Python code for Abaqus 2019 was developed for calculating the interlaminar energy release rate (G) values for a range of pre-crack lengths at different interfaces of the AP laminate, when no binding was applied. The slice model technique proposed in [1], and represented in Figure 1, was used to achieve high accuracy while reducing computation weight. The interface with higher G values was determined to be the most probable to delaminate (critical interface).

The additive binding layup selected was  $[\pm 45]_s$ . Figure 2 shows a comparison of the G values at the critical interface for both cases with and without binding. The G was reduced by 70%. Experimentally, the tensile failure strain and load of the laminate were increased by about 50%. Thus, this technique suppresses delamination successfully.

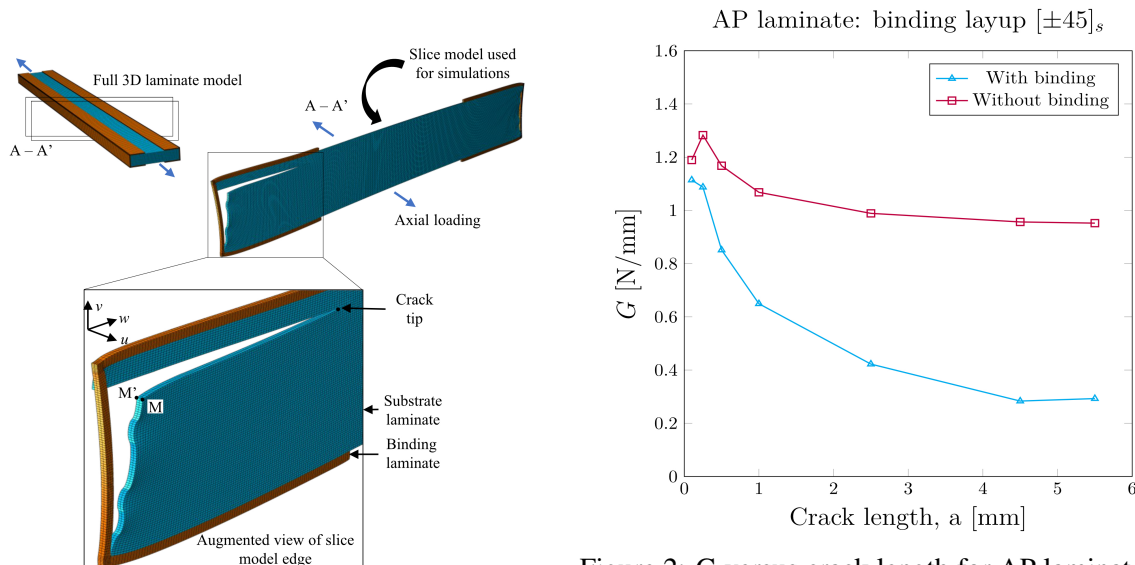


Figure 1: Slice model used with binding applied.

Figure 2: G versus crack length for AP laminate at the critical interface.

## References

- [1] W.G. Jiang, J.L. Henshall (2006) Analysis of composite laminate beams using coupling cross-section finite element method. *Applied Mathematics and Mechanics*, **27**, 1709–1718.