

## ANALYSIS OF RADAR ABSORBING FSS ON FOLDCORES AND HONEYCOMBS

J.J.P. VAN ES<sup>\*</sup>, A. HULZINGA<sup>\*</sup>, P. TENSEN<sup>\*</sup>, H. SCHIPPERS<sup>\*</sup>,  
R.M.H. HEIJMANS<sup>†</sup>, M.J.G. JOURNEE<sup>†</sup>

<sup>\*</sup> Netherlands Aerospace Centre (NLR)  
Voorsterweg 31, 8316 PR Marknesse, The Netherlands  
e-mail: Jan-Joris.van.Es@nlr.nl, www.nlr.nl

<sup>†</sup> Teijin Aramid B.V.  
Velperweg 76, 6824 BM Arnhem, The Netherlands  
email: Ruud.Heijmans@Teijinaramid.com, www.teijinaramid.com

**Key words:** Computational Methods, Metamaterials, Radar absorption

**Abstract:** The objective of the paper is to investigate the radar absorption of honeycombs and foldcores with printed conductive patterns. These structures can be manufactured by first printing conductive Frequency Selective Surfaces (FSS) on planar substrates, which then can be used to shape foldcores and honeycombs by means of specific manufacturing technologies. Foldcores can be considered as intermediate shapes between planar sheets (where the printed patterns are perpendicular to the impinging radar waves) and honeycombs (where the printed patterns are parallel to the impinging radar wave). It is shown that the radar absorbing properties of the design strongly depend on the electrical conductivity of the paint, the size of the printed patterns and the orientation of the printed patterns with respect to the impinging wave. It is shown that a planar FSS has a maximum absorption of 50%, while foldcores and honeycombs may obtain a higher absorption due to the fact that the patterns are orientated under an angle with respect to the propagation direction of the wave.

### 1 INTRODUCTION


This research deals with the development of advanced radar absorbing structures with artificial structured metamaterials. These materials can be realised by printing arrays of electrically conducting patterns (such as Split-Ring resonators) on non-conducting sheets. The goal of the conducting patterns is to modify the EM properties of the structure and to influence the way incident EM waves are reflected and transmitted. The structure can be made lossy, i.e. absorbing EM energy, by applying the right patterns and right electric conductivity.

The challenge is two-fold. There is the question of how the conducting patterns should look and what size they should have in order to obtain the desired EM properties. On the other hand there is the question of actually fabricating such a structure. Screen printing and inkjet printing with electrically conducting ink appear valid options to produce the desired shapes. The substrates can be FR4 glass epoxy, aramid honeycomb papers, or other non-conducting sheets. Once successful the printed 2D sheets can be used to create 3D structures such as honeycombs and foldcores with tailored EM properties.

The subject of tailoring the EM properties of 3D arrangements of electrically conducting patterns is not new and has been the topic of earlier research [1,2,3]. In these earlier publications the emphasis is on achieving particular values of permittivity and permeability. In the current work we focus on the radar absorbing properties of the materials and the optimisation of the conductivity to maximise absorption.

## 2 GEOMETRIES

The electrically conducting patterns in this research are circular rings and split-ring resonators (SRR). The conducting patterns are repeated in a regular way to form an infinite sheet. Depending on the orientation of the pattern in the unit cell and the repetition vector, the sheet can be an infinitely thin FSS, a honeycomb or a foldcore (Figure 1).

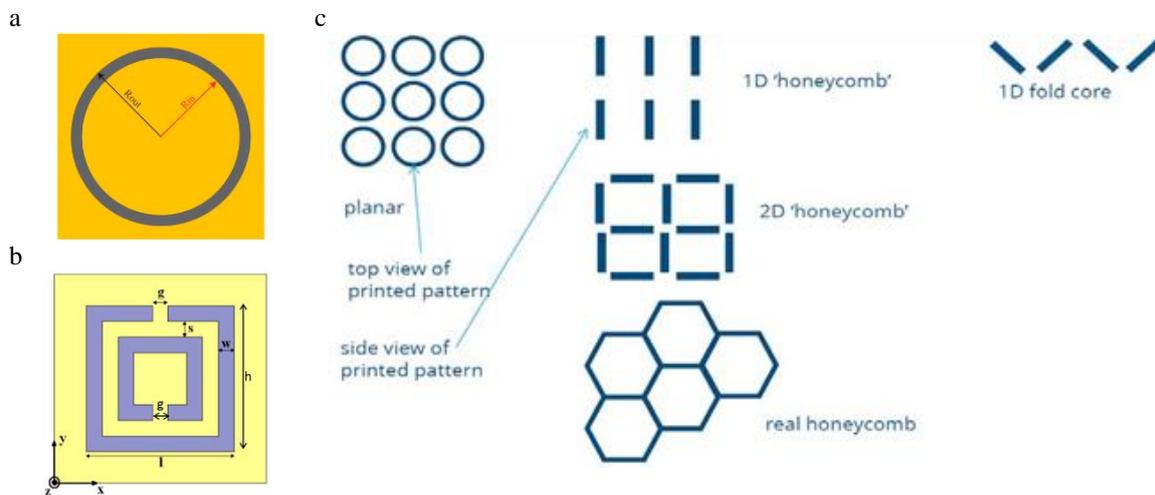

**Figure 1:** Conducting patterns ring (a) and split-ring resonator (SRR) (b). Extension of primary periodic cells to sheets, honeycombs or foldcores (c)

## 3 SIMULATION RESULTS

The electromagnetic properties of the conducting patterns are determined by simulating the interaction between an infinite sheet of repeated patterns and impinging planar waves. The reflection and transmission coefficients of the waves due to the presence of the sheet are simulated in Ansys HFSS. In this software package a single conductive element embedded in a unit cell with periodic boundary conditions generates the regular array. In the simulations only the conductors are considered. Substrates, part of any practical material, are ignored as they are thin and have little impact on the final EM properties.

### 3.1 Size

The size and the exact shape of the conducting patterns determine the resonant behaviour. In the current work the conducting patterns are designed for maximum effect in X-band (8.2-12.4 GHz). The SRR has a 4 mm width ( $l$ ), 3 mm height ( $h$ ), 0.5 mm spacing between the rings ( $s$ ), 0.5 mm gap ( $g$ ) and 0.3 mm trace width ( $w$ ). The conducting rings have an inner radius of 4.2 mm and an outer radius of 4.8 mm (Figure 1 a and b).

### 3.2 Electric conductivity


The impinging EM waves induce currents in the conducting patterns. These currents experience Ohmic losses which gives rise to the radar absorbing effect. The rings need to have a specific conductivity for optimum absorption. If the electric conductivity is too high currents will be induced in the patterns, but the currents will experience little losses. If the conductivity is too low little currents will be induced and the waves will propagate unobstructed. The absorption,  $A$ , is calculated from the (complex-valued) transmission,  $T$ , and reflection,  $R$ , coefficients in the HFSS simulation results as

$$A = 1 - RR^* - TT^* \quad (1)$$


To illustrate the importance of the value of the conductivity, the reflection and transmission coefficients have been computed for perfectly conducting rings in a planar sheet FSS. The results are shown in **Figure 2**. Obviously the rings are resonant at 12 GHz. For these perfectly conducting rings there is no absorption. Next the absorption coefficient is computed in relation to the conductivity of these rings. From **Figure 3** it is concluded that the amount of absorption strongly depends on the conductivity. The conductivity of the rings can be quantified in different ways. It can be given as the sheet resistivity ( $R_s$ ), the parallel resistance ( $R_{||}$ ) of two half rings when measured across with two probes or as the resistance of the whole ring when it would be interrupted by an infinitely narrow slit ( $R=4 R_{||}$ ).  $R_s$  and  $R_{||}$  relate as

$$R_{||} = R_s (\pi/4) (r_o + r_i) / (r_o - r_i) \quad (2)$$

For the given size of the rings, simulations show that the optimum absorption is obtained for  $R_{||}=140 \Omega$  and  $R_s=12 \Omega/\text{sq}$ .  $R_{||}$  is almost frequency invariant.

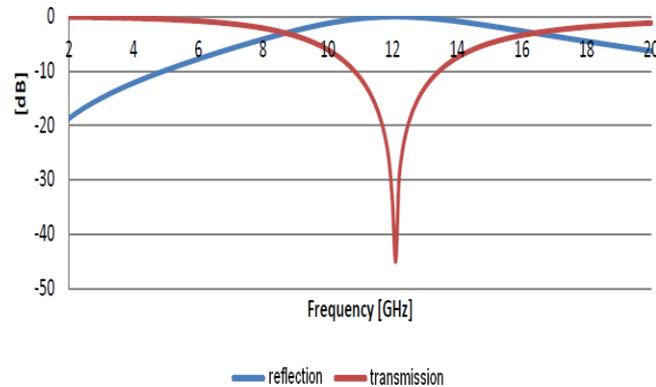

**Figure 2:** Reflection and transmission coefficient of planar sheet with perfectly conducting rings; (inner radius : 4.2 mm, outer radius 4.8 mm, cell size 11 mm)

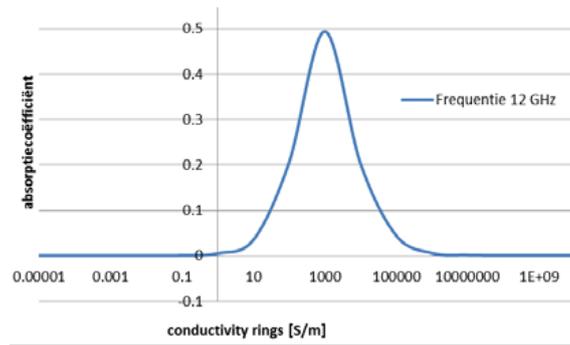

**Figure 3:** Absorption coefficient of planar sheet with conducting rings at 12 GHz as function of the bulk conductivity of the rings


### 3.3 Orientation

For planar sheets of conducting patterns with zero thickness the maximum absorption is found to be 0.5 (-3 dB) (**Figure 3**). Using transmission line theory, this case can be modelled as a lumped impedance  $Z_L$  in parallel with the wave impedance of the propagation medium  $Z_0$ . In this case the reflection and transmission coefficients are given as


$$R = -Z_0 / (Z_0 + 2Z_L) \quad (3)$$

$$T = 2 Z_L / (Z_0 + 2Z_L) \quad (4)$$

such that indeed the absorption is 0.5 when  $Z_L = Z_0/2$ . Only in the case when the conducting patterns are oriented out-of-plane higher absorption is observed.

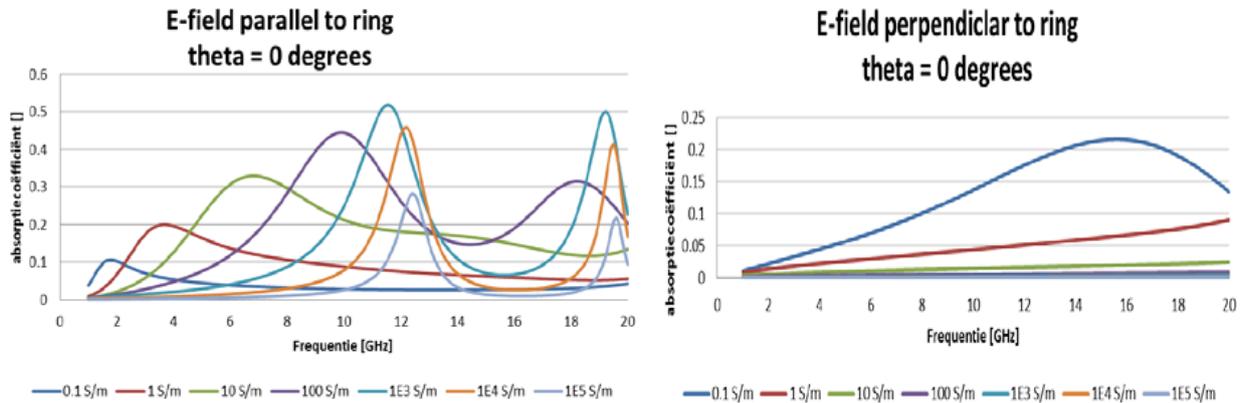

**Figure 4:** Absorption of 1D honeycomb with rings for different conductivities; direction E-field parallel to the rings (left), direction of E-field perpendicular to the rings (right)

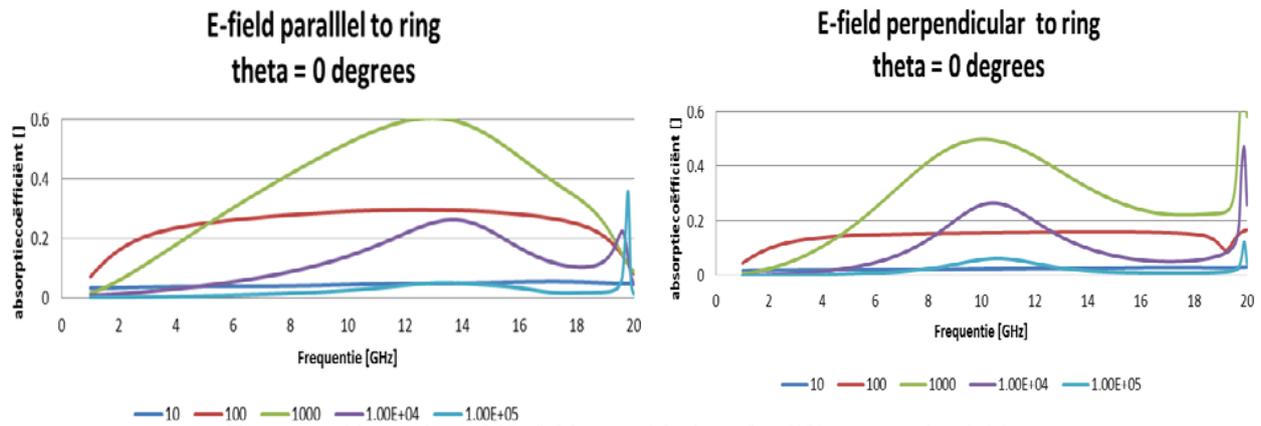

**Figure 5:** Absorption of 1D foldcore with rings for different conductivities; direction E-field parallel to the rings (left), direction of E-field perpendicular to the rings (right)

The orientation of the conducting patterns with respect to the E-field of the impinging influences the magnitude of the induced current in the patterns and thus the absorption. The induced current and the losses are largest with the conductors parallel to the electric field vector. This effect is nicely illustrated in a 1D honeycomb with conducting rings (**Figure 4**). The different colours in this figure indicate different values of the conductivity. Generally the variation in absorption is smaller in foldcores, because the patterns are oriented in two or more angles out of plane (**Figure 5**).


## 4 FABRICATION OF TEST SAMPLES

### 4.1 Foldcores

Samples of foldcores with conducting patterns were made to allow RF measurements of the absorbing properties (**Figure 6**). First the conducting patterns were printed on 54 g/m<sup>2</sup> aramid paper which was impregnated with 61 g/m<sup>2</sup> phenolic resin to a total weight of 115 g/m<sup>2</sup>. The patterns were applied with 120 mesh screen printing of electrically conducting ink. The conductivity of the patterns was tuned to the desired value by blending a low and a high-conductivity ink to the desired value. In some cases the conductivity of the patterns was increased by printing multiple (two) layers of the same ink.

After printing and drying, the paper was folded into the desired foldcore shape or honeycomb shape. Finally the foldcores were cured for about 1 hour at 150°C to secure the shape. The curing also improved the conductivity of the printed patterns. The exact curing duration and temperature were used to optimise the conductivity.

Finally, the conductivity of the conducting rings was characterized through measurement of the resistance ( $R_{||}$ ) between the two sides of the rings using a two-probe method. The ring resistance typically shows a variation in the order of 10%. The foldcore samples have a size of about 25 x 16 cm and a height of 2 cm.

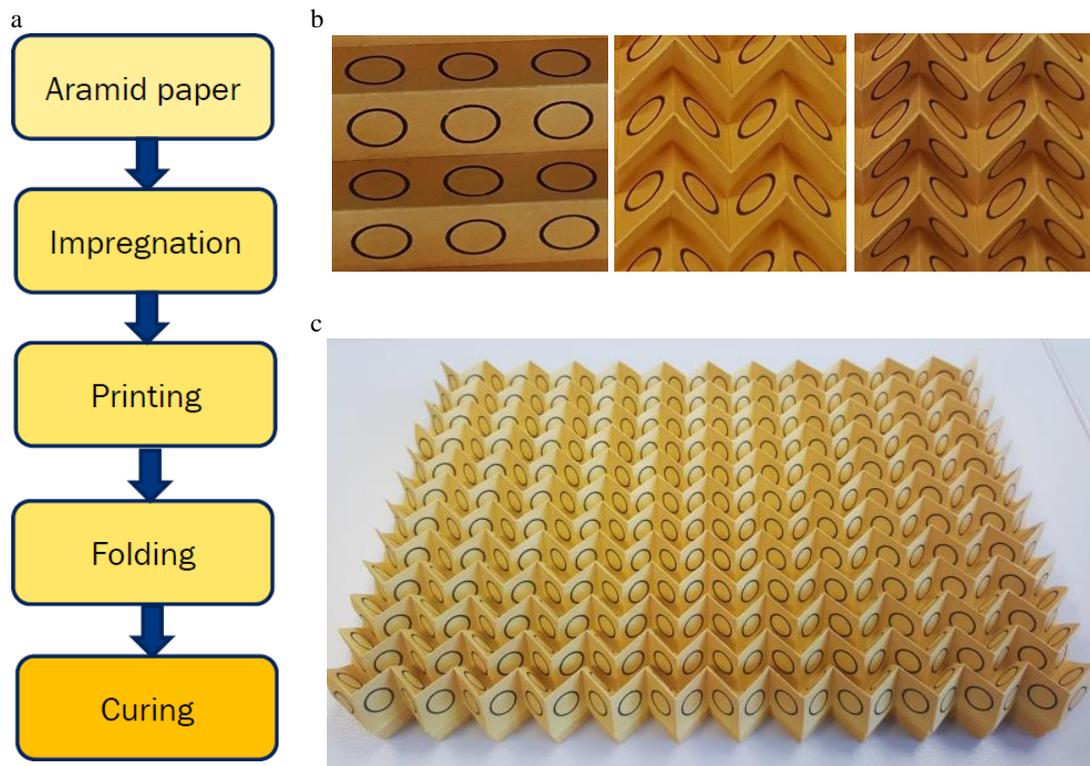

**Figure 6:** Foldcore and honeycomb fabrication  
a: fabrication process, b: different printing and folding patterns, c : final product

## 4.2 Honeycombs

Honeycomb samples with SRRs were fabricated in a similar way as the foldcore samples. The honeycombs were folded from a single printed sheet (unlike in large-scale honeycomb fabrication). The samples measure 7.5 cm x 4 cm and have a thickness of 0.5 cm. Samples with carbon ink (236 Ohm/sq) and silver ink (0.05 Ohm/sq) were made (**Figure 7**).




**Figure 7:** Honeycomb samples with SRR rings  
in carbon (left) and silver ink (right)

## 5 MEASUREMENT RESULTS

Both foldcore and honeycomb samples were measured in the frequency range between 1 and 20 GHz in free-space reflection-transmission setups to determine the absorption. For these measurements six foldcore samples were combined in a single panel of 50 cm x 50 cm


on a Styrofoam substrate. The honeycomb samples were measured individually, placed in an aperture in an absorbing plate (**Figure 8**). All measurements were performed with normal incidence.

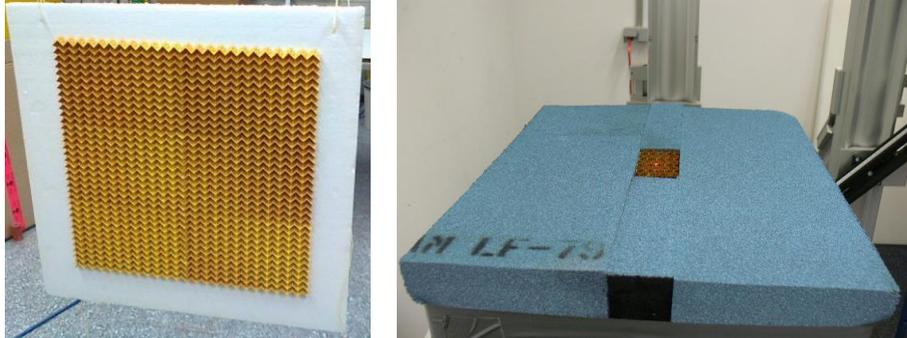

**Figure 8:** Final 50x50 cm foldcore panel (left) and honeycomb sample (right) during measurement

## 5.1 Foldcores


Foldcore samples with rings with two different conductivities ( $120 \Omega/\text{sq}$  and  $12 \Omega/\text{sq}$ ) were fabricated and measured (**Figure 9**). The conductivity of  $12 \Omega/\text{sq}$  is approximately optimal and yields an absorption of 0.55; nearly the simulated value of 0.6. The maximum is found for HH polarization where the E-field vector is best aligned with the conducting patterns. The conductivity of  $120 \Omega/\text{sq}$  is sub-optimal and yields reduced absorption.

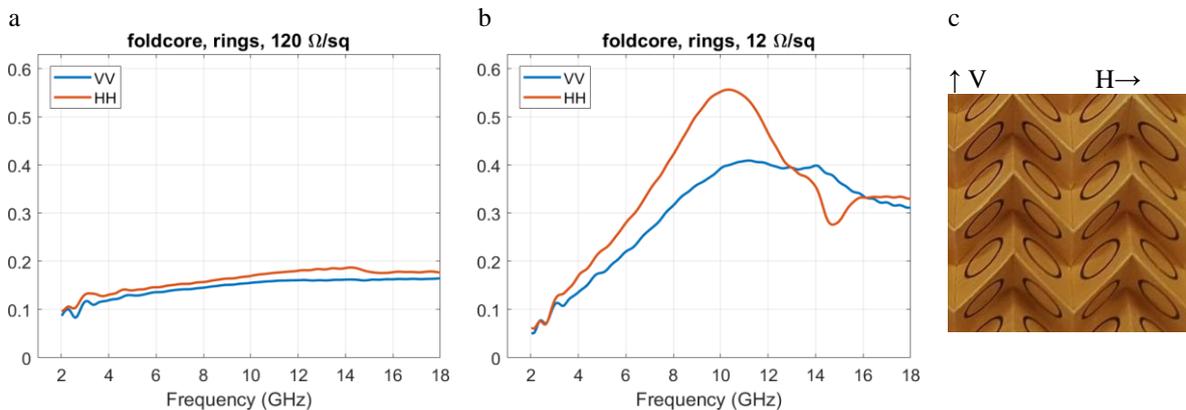

**Figure 9:** Measured absorption in (a) foldcore with rings  $R_s = 120 \Omega/\text{sq}$  and (b) foldcore with rings  $R_s = 12 \Omega/\text{sq}$ . The polarization is indicated in (c).

## 5.2 Honeycombs

The honeycomb measurement results show the importance of the conductivity of the patterns (**Figure 10**). The carbon ink ( $236 \Omega/\text{sq}$ ) has too low conductivity to yield a significant effect and the radar wave passes through the sample without much interaction. The high conductivity silver ink ( $0.05 \Omega/\text{sq}$ ) makes visible the double resonant structure of the SRR. It has a maximum absorption of 0.67 (-1.7 dB) with HH polarization at 9.65 GHz.

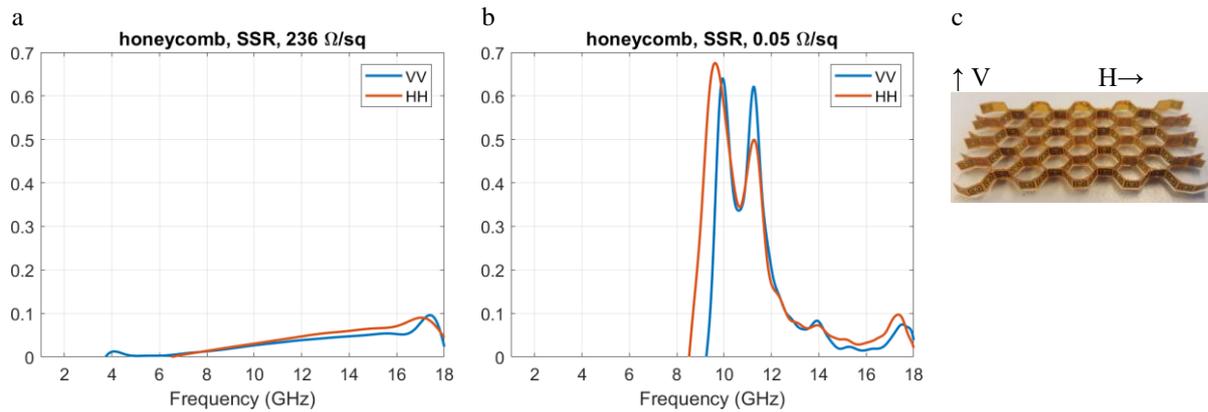

**Figure 10:** Measured absorption (A) of honeycomb with SRR in carbon ink (236  $\Omega/\text{sq}$ ) (a) and in silver ink (0.05  $\Omega/\text{sq}$ ) (b). The polarization is indicated in (c).

## 6 CONCLUSIONS

This paper investigates radar absorbing structures based on foldcore and honeycomb sandwich cores with printed electrically conducting patterns. RF absorption is created by Ohmic losses of currents induced in the patterns. To achieve optimal absorption it is necessary that the E-field of the incident wave is parallel to the conducting pattern and that the conductivity has a specific value. Honeycomb and foldcore samples with patterns with the desired conductivity were fabricated and measured. The samples were shown to have high losses. The lossy foldcore and honeycomb materials can be used as core materials to produce lightweight structures with tailored EM properties. The current work focused on conducting patterns consisting of SRRs and rings resonant at X-band. The patterns can be engineered to further optimise the EM properties at X-band or at other frequencies.

## 7 ACKNOWLEDGEMENTS

The authors acknowledge the kind support from Matthias Jansen (Airbus Defence and Space) in the measurement of the honeycomb samples.

## REFERENCES

- [1] Diaz, Rodolfo E. *Material with artificial dielectric constant* United States Patent 5662982, 2 Sept 1997.
- [2] Houck, Andrew A.; Brock, Jeffrey B.; Chuang, Isaac L. *Experimental observations of a left-handed material that obeys Snell's law* Phys. Rev. Lett. 90(13), 137401, 2003.
- [3] Ekmekci E.; Turhan-Sayan G. *Comparative investigation of resonance characteristics and electrical size of the double-sided SRR, BC-SRR and conventional SRR type metamaterials for varying substrate parameters* Progress In Electromagnetics Research B, Vol. 12, 35-62, 2009.