

Pore Refinement Action of GGBFS and Fly Ash on the Primary and Secondary Capillary Imbibition Rates of Concrete

Natalia M. Alderete¹, Yury A. Villagrán-Zaccardi² and Nele De Belie¹

¹ Magnel Laboratory for Concrete Research, Ghent University, Technologiepark-Zwijnaarde 60, 9052-Gent, Belgium, nataliamariel.alderete@ugent.be, nele.debelie@ugent.be

² LEMIT, CONICET, Av. 52 entre 121 y 122 s/n, B1900AYA-La Plata, Argentina, yuryvillagran@conicet.gov.ar

Abstract. *Capillary imbibition is a transport phenomenon occurring in concrete structures exposed to weathering, frequently in direct connection with the resistance against different deterioration processes. This property depends on the volume and connectivity of pores. For ground granulated blast-furnace slag (GGBFS) and fly ash blended concrete mixes, the pore refining action of these supplementary cementitious materials plays a positive role in the disconnection of the capillary porosity and consequent reduction of the capillary imbibition rate. Moreover, for this particular transport process, primary and secondary transport rates can be defined in connection with different driving mechanisms. This allows a complementary description of the pore structure of concrete. In this paper, blended concrete mixes were prepared by substituting 20, 40 and 60 % of OPC by GGBFS, and 20, 30 and 40 % of OPC by fly ash. The pore structure of these concretes is assessed by water absorption under vacuum and mercury intrusion porosimetry after curing periods of 28 and 90 days. Long-term capillary imbibition tests were also performed and primary and secondary imbibition rates are computed by a novel approach that considers their linear evolution with the fourth root of time. Results show the refinement action of GGBFS and fly ash by a softening in the transition stage between the primary and secondary imbibition periods. A low water flow rate is consequently correlated with the increased tortuosity of samples.*

Keywords: *Sorptivity, Supplementary Cementitious Materials, Pore Structure, Imbibition.*

1 Introduction

Sorptivity is a widely used durability index of concrete. The quantification of the rate of water imbibition by capillarity in concrete describes the pore connectivity of cementitious materials. Previous work has shown that primary and secondary imbibition rates can be used for describing the pore structure on the basis of their corresponding driving mechanism.

The most usual assessment method considers the relation between water uptake and the square root of time, but it faces the significant difficulty of the lack of linearity of this relationship for the case of cementitious materials. This is usually referred as anomalous sorptivity (Hall, 2007; Küntz and Lavallée, 2001; Lockington and Parlange, 2003; Villagrán Zaccardi *et al.*, 2017). A comprehensive analysis of this anomaly led to the proposal of a new approach considering the fourth root of time, which was validated with experimental data in the short term (Villagrán Zaccardi *et al.*, 2017). The new model considers the swelling of the C-S-H gel as the main cause for the anomalous behaviour. Physical evidence of this swelling was recently presented in (Alderete *et al.*, 2019b), where the volumetric stability of mortar and concrete samples was registered using strain gauges.

During long-term exposure of samples, water uptake further continues at a very low rate even after the capillary rise has covered the full height of samples (Alderete *et al.*, 2019a; Bentz *et al.*, 2001; Castro *et al.*, 2011; Hall and Hoff, 2009; Kaufmann and Studer, 1995; Spragg *et al.*, 2011). A secondary imbibition period for the water ingress driven by diffusion into the finest pores of the cementitious matrix can be therefore defined. Allegedly, this process starts as soon as the material makes contact with water, but it is initially masked by the capillary action which dominates the water flow during the primary imbibition. The secondary capillary imbibition has been presented as a convenient complementary descriptor of the transport properties of cementitious materials (Henkensiefken *et al.*, 2009; Kurtis *et al.*, 2016; Liu and Hansen, 2016; Wei *et al.*, 2017). Both primary and secondary mechanisms should be considered for describing the whole moisture transport during imbibition.

In this paper, capillary imbibition tests were conducted for 17 weeks on concrete mixes with and without ground granulated blast furnace slag and fly ash to determine the primary and secondary capillary imbibition rates. These transport parameters are compared with the pore size distribution obtained by mercury intrusion porosimetry (MIP).

2 Materials and Methods

Concrete mixes were designed with a water to binder ratio (w/b) of 0.45. OPC type CEM I 42.5 N, ground granulated blast furnace slag (SB), and fly ash (FA) were used supplementary cementitious materials (SCMs) in partial replacement of OPC in proportions of 20, 40 and 60, and 20, 30 and 40%, respectively. A reference mix with only OPC as binder was also made. Table 1 displays the properties of the binders, including composition, density, and particle size distribution (obtained by laser diffractometry with optimal optical parameters chosen as suggested in (Alderete *et al.*, 2016)). Mix proportions, slump, air content, and compressive strength are provided in Table 2. The mixes were named based on the binder (OPC for control, SB, and FA for the blends) and the weight percentage of cement replacement. To improve the workability, a commercially available polycarboxylic ether-based superplasticiser was added to the concrete during mixing. In addition to five concrete cylinders with 10 cm in diameter, three 10 cm cubes for compressive strength were also cast for each mix and cured in a conditioned room at 20 °C ± 2 °C and 95 % ± 5 % RH for 28 and 90 days.

Table 1. Properties of OPC, SB, and FA. (nd = not determined, LOI = loss on ignition).

Properties	OPC				SB				FA			
Chemical composition (%)	CaO	64.67	S	nd	CaO	38.34	S	1.4	CaO	3.02	S	nd
	SiO ₂	20.74	Fe ₂ O ₃	1.52	SiO ₂	33.7	Fe ₂ O ₃	0.43	SiO ₂	54.19	Fe ₂ O ₃	7.92
	MgO	0.95	K ₂ O	0.77	MgO	8.18	K ₂ O	0.34	MgO	1.92	K ₂ O	3.38
	Al ₂ O ₃	4.91	MnO	nd	Al ₂ O ₃	11.36	MnO	8.18	Al ₂ O ₃	23.5	MnO	nd
	Na ₂ O	0.27	Cl ⁻	0.07	Na ₂ O	0.35	Cl ⁻	0.01	Na ₂ O	0.39	Cl ⁻	<0.01
	SO ₃	2.96	LOI	nd	SO ₃	0.03	LOI	0.16	SO ₃	0.94	LOI	1.84
Density (g/cm ³)	3.11				2.88				2.14			
Particle size dv10/50/90 (µm)	4.9/20.1/58.5				1.8/13.9/35.0				0.4/10/61.7			

Table 2. Nomenclature, mix composition, air content and slump of the studied concrete mixes.

	OPC _c	SB20 _c	SB40 _c	SB60 _c	FA20 _c	FA30 _c	FA40 _c
Cement - CEM I 42.5 N (kg/m ³)	342	274	205	137	274	239	205
SCM (kg/m ³)	0	68	137	205	68	103	137
Water (kg/m ³)	154	154	154	154	154	154	154
Sand (kg/m ³)	865	860	860	860	860	860	855
Gravel 2/8 (kg/m ³)	500	497	495	493	497	493	490
Gravel 8/16 (kg/m ³)	540	535	535	535	535	535	530
Air content (%)	2.1	2.4	2.1	2.3	2.8	2.3	2.4
Slump (mm)	70	70	100	120	70	100	150
Compressive strength 28d (MPa)	50.6	42.6	32.6	32.2	50.1	50.8	48.8

The top halves of the five cylinders were used to determine water absorption by immersion. First, samples were submitted to vacuum for 2 h and then water was drawn into the vacuum chamber until the sample became fully immersed. After 24 h samples were removed and the saturated weight was registered. Then, samples were subjected to drying in an oven at 105 °C. Finally, water absorption was calculated from the difference between the saturated weight and the dry weight, relative to the dry weight.

The samples for MIP were approximately 125 mm³, obtained from the core of one cylinder per mix. Microstructural damage during pre-conditioning was minimised by first drying samples at 40 °C for 24 h, and then vacuum-drying them at (20 ± 2) °C for two weeks at 0.1 bar (Snoeck *et al.*, 2014; Zhang and Scherer, 2011). The maximum applied pressure was 200 MPa in order to avoid massive cracking induced by the pressure (Beaudoin and Marchand, 2001). Measurements were corrected with a blank to disregard differential mercury compression. The intruding volume of mercury into the sample is a function of the pressure increase. Results are interpreted with the theoretical simplified model of cylindrical pores and translated into pore ‘diameters’ upon the application of the Lucas-Washburn equation. The surface tension and contact angle considered for these computations were 0.482 N/m and 142° (Ma, 2014), respectively. Qualitative contrasts are finally possible by comparing the threshold diameter (d_{th}) and intrudable pore volume (ϕ_{in}) (Ma, 2014). The calculation of d_{th} was made by the tangent method, and therefore denoted as d_{tg} (Liu and Winslow, 1995), corresponding to the intersection of tangent lines on the cumulative distribution curve at the smallest diameter that did not exhibit significant intrusion and the largest diameter that did. The range of the points to be fitted was determined by the analysis of the second derivative in the differential curve. Furthermore, according to the cumulative curve shape obtained, it is possible to make inferences about the presence of choke points.

The tested samples for the long-term capillary imbibition tests were obtained by sawing the section between 3 and 8 cm from the base of the five cylinders. Samples were laterally covered with aluminum-butyl tape to ensure one dimensional flow. The preconditioning procedure consisted in 72 h immersion in water and then drying in an oven at 50 °C until mass decrease was lower than a mass fraction of 0.1 % within 24 h. The capillary imbibition test consisted in putting the samples in contact with water, with an immersion depth of (3 ± 1) mm. Water evaporation was avoided by putting a lid on top of the water container. The water

level was checked regularly and the immersion depth was kept at (3 ± 1) mm during the whole testing period. Samples of OPCc and FA20c mixes with 28 days of curing were the first ones to be tested, with testing periods up to 10 weeks. Based on these results, it was decided to continue the measurements for the capillary imbibition tests on the rest of samples up to 17 weeks to obtain a larger amount of data for the secondary period than for the first data series. In this manner, a more complete description of the secondary period was achieved in those cases. Measurements were performed after exposure periods of 0.5 h, 1 h, 2 h, 3 h, 4 h, 5 h, 6 h, and 24 h and after that every 24 h during the first week, once a week during the first two months, and once a month until 4 months.

3 Results and Discussion

Figure 1 displays the results of relative water absorption of the mixes at 28 and 90 days. At 28 days, values of water absorption of all SB mixes are higher than the OPCc mix. However, at 90 days, mixes SB20c and SB40c had lower water absorption than OPCc at 90 days. Values of water absorption at 28 days increased slightly with the FA content. At 90 days, FA20c and FA30c show similar results as OPCc, but the higher replacement in FA40c does not allow to compensate the dilution effect.

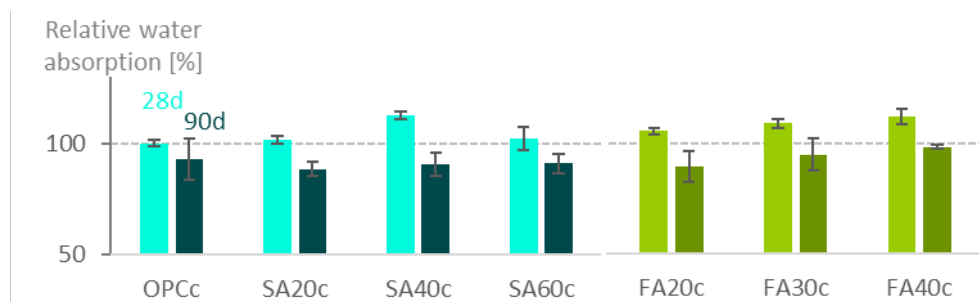


Figure 1. Relative open porosity and relative water absorption of OPCc, SB and FA concrete mixes at 28 and 90 days.

The cumulative mercury intruded volume curves of SB and FA mixes at 28 and 90 days are presented in Figure 2, with the indication of the ϕ_{in} and d_{tg} of each mix. Results reveal the refinement action of SB with time. All mixes had a reduction of ϕ_{in} between 16 % and 26 % after 90 days. Accordingly, d_{tg} values were reduced from 28 to 90 days. For FA mixes, results indicate the slower reaction of FA in comparison with SB, as indicated by reactivity tests (Alderete, 2018). Although all FA mixes have a lower ϕ_{in} at 90 days than at 28 days, the reduction is around half of that found for concrete mixes with SB. In fact, FA40c at 90 days displays a higher value than SB60c at 28 days. This shows that even with a lower amount of replacement ($40 < 60$) and with more time to react ($90 > 28$), FA does not compensate the clinker dilution as well as SB. Values of d_{tg} are in agreement with this as well, as they are higher for FA concrete mixes than SB mixes at 90 days.

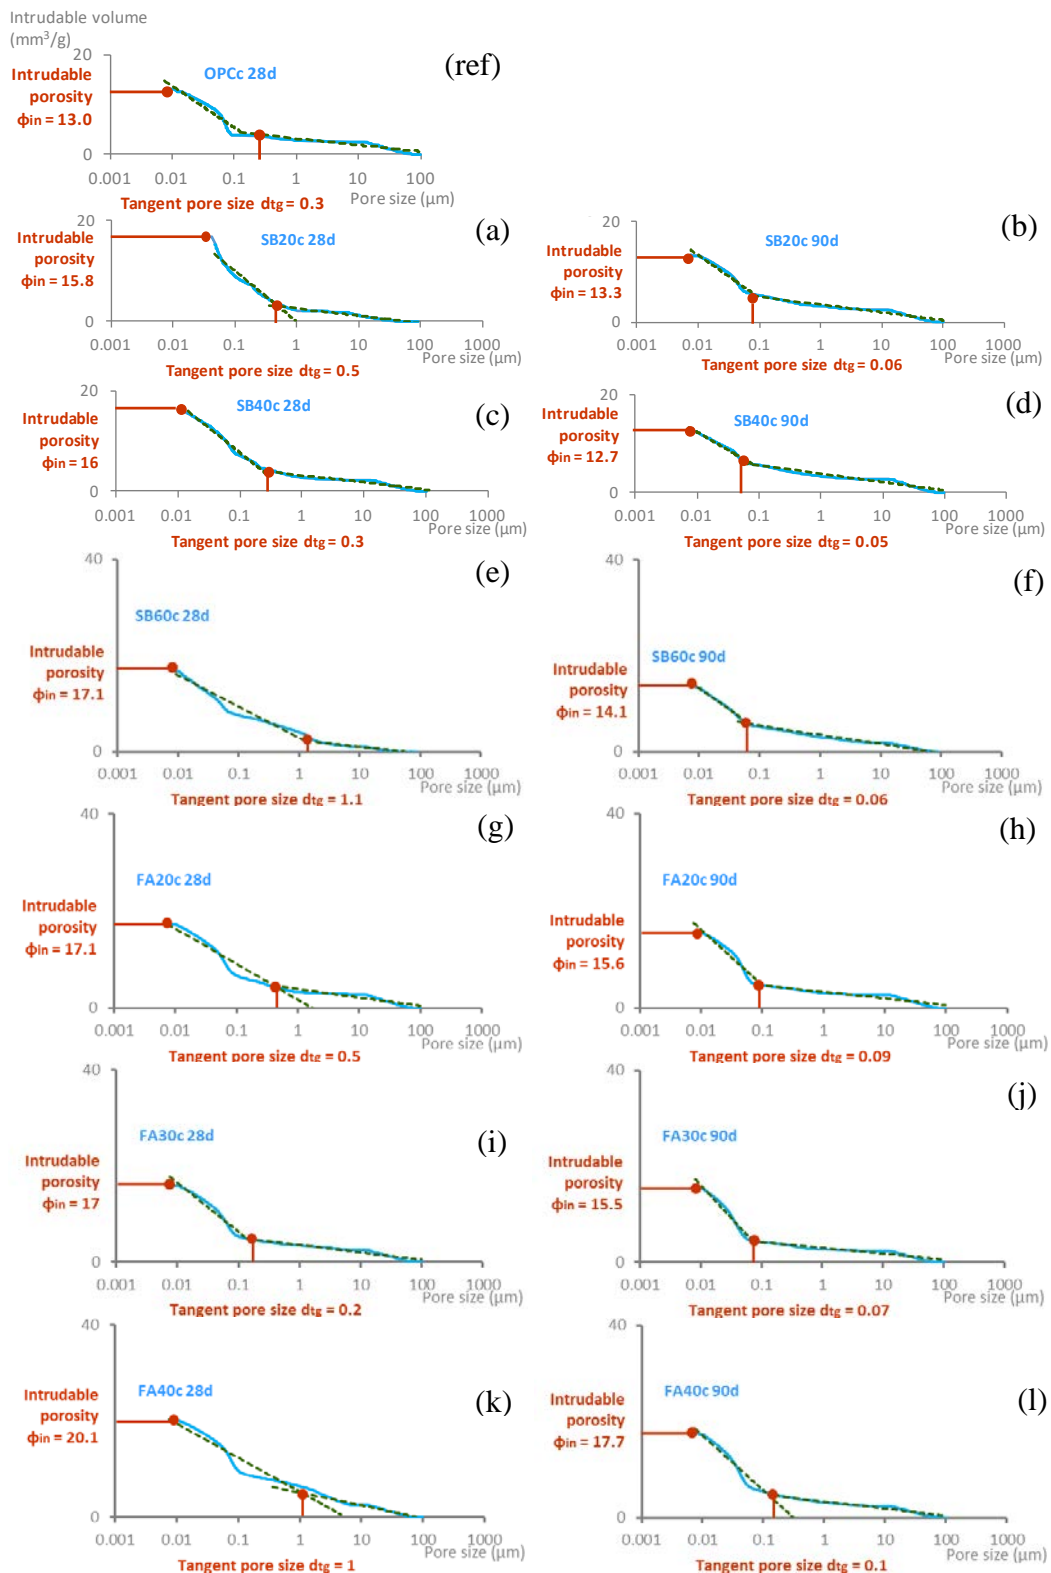


Figure 2. MIP curves of OPCc at 28 (ref), SB20c at 28 (a) and 90 (b), SB40c at 28 (c) and 90 (d), SB60c at 28 (e) and 90 (f), FA20c at 28 (g) and 90 (h), FA30c at 28 (i) and 90 (j), and FA40c at 28 (k) and 90 (l) days.

Results for the capillary imbibition of the mixes are shown in Figure 3. Two periods, primary and secondary, and a transition period in between, are observed. The primary imbibition period takes place within 1 and 3 weeks, for samples tested at 28 days and 90 days, respectively. Error bars represent the standard deviation ($n = 5$) and are marked in all graphs, but, as the variability was very small, some error bars are not visible because they are smaller than the marker. The capillary imbibition rate (CIR) is computed as the slope of the fitting line during the first week: CIR_{1w} (for 28 days); and during the first 3 weeks: CIR_{3w} (for 90 days). The secondary capillary imbibition rate is computed as the slope of the fitting line after the transition period: $sCIR_{1w}$ (for 28 days); and $sCIR_{3w}$ (for 90 days). The corresponding coefficients of determination are shown in the graphs. The transition period is highlighted in the graphs, where the difference between the primary and the secondary periods is less marked for blended than control concrete.

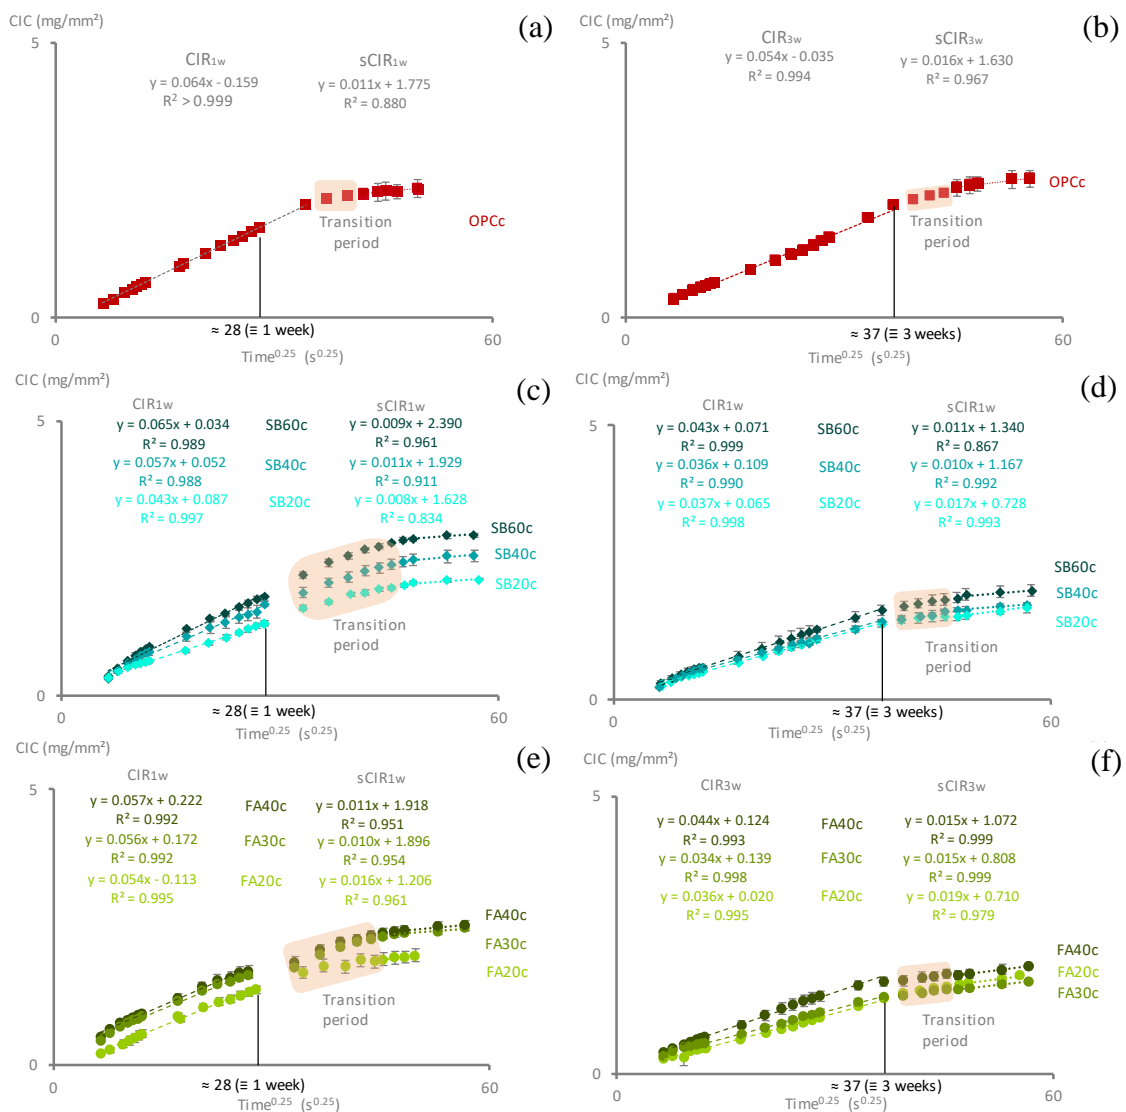


Figure 3. Long-term capillary water uptake results of OPCc at 28 (a) and 90 (b), SB at 28 (c) and 90 (d), and FA at 28 (e) and 90 (f) days.

Pore refinement due to the action of the SCMs led to a decrease in d_{tg} in the range of 0.2 to 1 μm at 28 days, to the range of 0.05 to 0.1 μm at 90 days, which corresponds to a decrease in the CIR from the range of 0.048 to 0.065 $\text{mg}\cdot\text{mm}^{-2}\cdot\text{s}^{-0.25}$ to the range of 0.034 to 0.044 $\text{mg}\cdot\text{mm}^{-2}\cdot\text{s}^{-0.25}$. This correlation is in contrast with the values of Φ_{in} , which are not reflecting so well the refinement action of the SCMs. Contrarily, the sCIR does not show a clear connection with the MIP parameters, and this transport parameter is likely linked with the content of C-S-H in each mix and the gel pores. Additional research in this regard seems valuable. Furthermore, blended concrete mixes had a more marked transition period and lower imbibition rate at 90 days in comparison with 28 days, which indicates a lower flow rate due to their increased tortuosity.

4 Conclusions

The long-term exposure of unsaturated samples involves additional water uptake after the capillary rise has covered the total height of samples. This is a process that occurs at a much slower rate than the short-term capillary imbibition, and it can be related to a secondary transport through the finest range of pores. Long-term capillary imbibition tests in blended concretes manifested the existence of primary and secondary periods. Both periods display increasing water uptake proportional to $t^{0.25}$.

The pore refinement action of ground granulated blast-furnace slag and fly ash was reflected in the comparable reduction of the CIR and d_{tg} parameters. In second term, Φ_{in} values were reduced from 28 to 90 days, but the correlation is not very good with the capillary imbibition. The likely reason is that pore refinement causes an increase in tortuosity more than a reduction in porosity. Lastly, sCIR does not reflect so well the refinement action of the SCMs. In this case, the transport parameter could be phenomenologically linked to the C-S-H content and its characteristic porosity.

Acknowledgements

Y. Villagrán-Zaccardi (MSCA - Seal of Excellence) and N. Alderete (12ZG820N) thank FWO-Vlaanderen for the financial support. Financial support from ANPCyT (PICT 2017-0091 Prest BID) is also appreciated.

ORCID

Natalia Alderete: <https://orcid.org/0000-0001-7967-1955>

Yury Villagrán-Zaccardi: <https://orcid.org/0000-0002-0259-7213>

Nele De Belie: <https://orcid.org/0000-0002-0851-6242>

References

- Alderete, N. M. (2018). *Microstructure of mortar and concrete with supplementary cementitious materials: relation with the capillary imbibition phenomenon*, PhD Thesis, UGhent and UTN.
- Alderete, N. M., Villagrán-Zaccardi, Y. A. and De Belie, N. (2019a). Mechanism of Long-Term Capillary Water Uptake in Cementitious Materials, *Cement & Concrete Composites*, submitted.
- Alderete, N. M., Villagrán-Zaccardi, Y. A. and De Belie, N. (2019b). Physical evidence of swelling as the cause of anomalous capillary water uptake by cementitious materials, *Cement and Concrete Research*, 120, 256–266. <https://doi.org/10.1016/j.cemconres.2019.04.001>
- Alderete, N. M., Villagrán Zaccardi, Y. A., Dos santos Coelho, G. S. and De Belie, N. (2016). Particle size distribution and specific surface area of SCMs compared through experimental techniques. In: *Proceedings of the International RILEM Conference on Materials, Systems and Structures in Civil Engineering*, Lyngby,

- Denmark, 61–72.
- Beaudoin, J. J. and Marchand, J. (2001). Pore Structure. In: *Handbook of Analytical Techniques in Concrete Science and Technology*, 528–628. <https://doi.org/10.1016/B978-0-8155-1437-4.50017-5>
- Bentz, D. P., Ehlen, M. A., Ferraris, C. F. and Garboczi, E. J. (2001). Sorptivity-based service life predictions for concrete pavements. In: *Proc. of the 7th International Conference on Concrete Pavements*, Orlando (FL), 1, 9–13.
- Castro, J., Bentz, D. and Weiss, J. (2011). Effect of sample conditioning on the water absorption of concrete. *Cement and Concrete Composites*, 33(8), 805–813. <https://doi.org/10.1016/j.cemconcomp.2011.05.007>
- Hall, C. (2007). Anomalous diffusion in unsaturated flow : Fact or fiction? *Cement and Concrete Research*, 37, 378–385. <https://doi.org/10.1016/j.cemconres.2006.10.004>
- Hall, C. and Hoff, W. (2009). Water transport in brick, stone and concrete. CRC Press, Boca Raton. <https://doi.org/10.1520/CCA10518J>
- Henkensiefken, R., Castro, J., Bentz, D., Nantung, T. and Weiss, J. (2009). Water absorption in internally cured mortar made with water-filled lightweight aggregate. *Cement and Concrete Research*, 39(10), 883–892. <https://doi.org/10.1016/j.cemconres.2009.06.009>
- Kaufmann, J. and Studer, W. (1995). One-dimensional water transport in covercrete - application of non-destructive methods. *Materials and Structures*, 28(2), 115–124.
- Küntz, M. and Lavallée, P. (2001). Experimental evidence and theoretical analysis of anomalous diffusion during water infiltration in porous building materials. *Journal of Physics D: Applied Physics*, 34, 2547–2554.
- Kurtis, K. E., Burris, L. and Alapati, P. (2016). Consider Functional Equivalence : A (Faster) Path to Upscaling Sustainable Infrastructure Materials Compositions. In *Proc. of the 1st International Conference on Grand Challenges in Construction Materials*, 8 p.
- Liu, Z. and Hansen, W. (2016). A geometrical model for void saturation in air-entrained concrete under continuous water exposure. *Construction and Building Materials*, 124, 475–484. <https://doi.org/10.1016/j.conbuildmat.2016.07.113>
- Liu, Z. and Winslow, D. (1995). Sub-distributions of pore size: A new approach to correlate pore structure with permeability. *Cement and Concrete Research*, 25(4), 769–778. [https://doi.org/10.1016/0008-8846\(95\)00067-M](https://doi.org/10.1016/0008-8846(95)00067-M)
- Lockington, D. A. and Parlange, J.-Y. (2003). Anomalous water absorption in porous materials. *Journal of Physics D: Applied Physics*, 36, 760–767. <https://doi.org/10.1088/0022-3727/36/6/320>
- Ma, H. (2014). Mercury intrusion porosimetry in concrete technology: Tips in measurement, pore structure parameter acquisition and application. *Journal of Porous Materials*, 21(2), 207–215. <https://doi.org/10.1007/s10934-013-9765-4>
- Snoeck, D., Velasco, L. F., Mignon, A., Van Vlierberghe, S., Dubruel, P., Lodewyckx, P. and De Belie, N. (2014). The influence of different drying techniques on the water sorption properties of cement-based materials. *Cement and Concrete Research*, 64, 54–62. <https://doi.org/10.1016/j.cemconres.2014.06.009>
- Spragg, R. P., Castro, J., Li, W., Pour-Ghaz, M., Huang, P.-T. and Weiss, J. (2011). Wetting and drying of concrete using aqueous solutions containing deicing salts. *Cement and Concrete Composites*, 33(5), 535–542. <https://doi.org/10.1016/J.CEMCONCOMP.2011.02.009>
- Villagrán Zaccardi, Y. A., Alderete, N. M. and De Belie, N. (2017). Improved model for capillary absorption in cementitious materials: Progress over the fourth root of time. *Cement and Concrete Research*, 100, 153–165. <https://doi.org/10.1016/j.cemconres.2017.07.003>
- Wei, Z., Falzone, G., Wang, B., Thiele, A., Puerta-Falla, G., Pilon, L., Neithalath, N. and Sant, G. (2017). The durability of cementitious composites containing microencapsulated phase change materials. *Cement and Concrete Composites*, 81, 66–76. <https://doi.org/10.1016/j.cemconcomp.2017.04.010>
- Zhang, J. and Scherer, G. W. (2011). Comparison of methods for arresting hydration of cement. *Cement and Concrete Research*, 41(10), 1024–1036. <https://doi.org/10.1016/j.cemconres.2011.06.003>